

# **CHARACTERIZATION OF CONCRETE BLENDED WITH SUGARCANE BAGASSE ASH**

**By**

**Kennedy Aburili**

[kenaburili@yahoo.com](mailto:kenaburili@yahoo.com)

Department of Disaster Preparedness and Engineering Management

Masinde Muliro University of Science and Technology (MMUST)

**R. O Onchiri**

Department of Civil and Structural Engineering

Masinde Muliro University of Science and Technology

**G, W Waswa**

Department of Disaster Preparedness and Engineering Management

Masinde Muliro University of Science and Technology

**Abstract**

Baggase is a cellulose fiber remaining after the extraction of the sugar-bearing juice from sugarcane. It is a valuable byproduct in sugar milling and is often used as a primary fuel source due to its high calorific value required to supply most energy requirement for most sugar factory operations. The burning of baggase leaves solid black particles known as sugar cane baggase ash. Utilization of waste material as mineral admixture in concrete provides a satisfactory solution to some of the economical, environmental and concerns associated with waste management. SCBA is normally disposed as landfills, exposure to these dusts causes chronic lung condition and its application on agricultural lands results to heavy metals concentrations in soils. It has been proved by several researchers that SCBA has intrinsic characteristic such as high content of silica in the form of quartz. This study mainly focused on SCBA disposed as solid wastes from Nzoia Sugar Company, Bungoma County in western Kenya. The research design adopted was Experimental. Granulometric indices of SCBA were determined through sieving the samples and weight retained. Strength Activity Index test, was used to assess the Pozzolanic activity of SCBA. This research showed that SCBA exhibits high Pozzolanic activity, hence can be used as a substitute cementitious material.

**Key words:** Sugar Cane Baggase Ash, Strength Activity Index, Silica, Nzoia Sugar Company, Pozzolanic Activity.

## **Introduction**

Concrete is one of the most commonly used construction material in the world. It's basically composed of three components: cement, water and aggregates. Dubey (2011) established that, combination of a number of ingredients such as Sugar cane baggase ash (SCBA) can generally be used in concrete production. Sugarcane is one of the major crops grown in over 110 countries and its total production is over 1500 million tons, this is according to Goyal *et al.* (2010). Baggase is a cellulose fiber remaining after the extraction of the sugar-bearing juice from sugarcane. The burning of baggase leaves solid black particles known as SCBA which are normally disposed as landfills, spread over farms or dumped in ash ponds. Arkarin, *et al.* (2013) observed that these landfills are a nuisance to communities surrounding industrial areas and are a frequent cause for resistance to industrial expansion and rehabilitation of sugarcane farmlands.

The objective of this study was to determine the Pozzolanic activity of SCBA, specifically from Nzoia Sugar Company (NSC), which is dumped as landfill. NSC, one of the eight sugar factories in Kenya is located in Bungoma County of Western Province with a nucleus and out-growers size of 3,400 and 27,000 Hectares respectively. It produces at-least 5,600 Tons of SCBA per month. All the engineering tests were done at Public Works Lab, Kakamega also in western Kenya.

The pozzolanic activity of the SCBA was determined based on compressive strength according to the procedures outlined in ASTM C311 (2004) and specified by ASTM C618 (1999). In this test, the 7 days and 28 days compressive strength of cement - SCBA mixture was compared to that without SCBA. Samples were prepared for each grain size of SCBA. The mixture (SCBA + cement) should provide at-least 75% of the strength of the control (cement only) at 7 day and 28

day. The water requirement and compressive strength for the strength activity indices were determined according to the procedure given in ASTM C109 (1993).

## **Materials**

SCBA samples were purposely selected from three dumping sites and the fourth sample was achieved by mixing the samples from the three sites. Different grain sizes were sorted to produce various SCBA samples. SCBA consists of particles with various shapes and sizes. The boiler furnace temperature was around 450°C. According to Cordeiro *et al.* (2010), burning baggase between 400°C and 600°C produces an increase in the Pozzolanic Activity Index due to loss of carbon during the calcination process. Cement used in this study was type 1 OPC, purposely procured locally. This cement binder complied with requirement of BS 12 (1996). Sand, free from debris was purposefully purchased locally. The sand particles were packed to give minimum void ratio and high voids content leading to requirement of more mixing water. The sand had a minimum size of 150micron to maximum particle size of 4.75 mm and was used as fine aggregate according to BS 812-103.2 (1989).

The water used was of drinking quality in accordance within the BS 3148 (1980) recommendations. In this study, casting and curing of specimens were done using potable water free from deleterious materials. Water plays an important role in concrete production. It starts the reaction between the cement and aggregates and helps in hydration of the concrete mix. The apparatus used to determine the grain size distribution of all the aggregates were; Balance, a set of sieves and an oven. The sieve sizes used were 75µm, 150µm, 300µm, 600µm, 1mm, 2mm, 3mm, 6mm, 7mm, 8mm, 9mm, 10mm, 14mm and 20mm. For determination of hydrometer analysis of sand, the material and apparatus used were: dispersing agent (sodium hexametaphosphate (40 g/L)) solution and an hydrometer.

## Methods

### (i) Grain Size Distribution

The particle size distributions of SCBA, OPC and ballast were determined using the ASTM D422 (2007) specifications. This method of test covers the requirements in addition to or superseding the requirements of AASHTO T 11 AND T 27 for the determination of the particle size distribution of fine and coarse aggregates. A weighed sample of dry aggregate was separated through a series of sieves of progressively smaller openings for determination of particle size distribution. This test method was used to separate particles into size ranges and to determine quantitatively the mass of particles in each range. These data were combined to determine the particle-size distribution (gradation). This test method used a square opening sieve criterion in determining the gradation of SCBA and OPC for sieve 5mm, 2mm, 1mm, 0.6mm, 0.3mm, 0.150mm, and 0.075mm. Sample processing adopted air drying method to obtain the various specimens.

This test method was also used to separate particles into size ranges and determine quantitatively the mass of particles in each range. As the particle size distributions are continuous, a total of 7 indices;  $D_2$ ,  $D_1$ ,  $D_{0.6}$ ,  $D_{0.3}$ ,  $D_{0.15}$ ,  $D_{0.075}$ , and  $D_{<0.075}$  were used to characterize the granulometric sizes of the SCBA samples and are the corresponding values representing samples retained on sieve size 2mm, 1mm, 0.6mm, 0.3mm, 0.15mm, 0.075mm and passing sieve 0.075mm respectively.

The portion for sieve analysis was obtained from the sample by the use of a sample splitter. Fine (SCBA) and course (ballast) aggregate were thoroughly mixed and in a dry condition prior to

splitting. The selection of a portion for test of an exact predetermined weight was not be attempted. However, the weight of the sample portion before sieving was also determined and recorded. All aggregates were sieved for 10 minutes. The weight of each sieve as well as the bottom pan to be used in the analysis was noted. In addition, the weight of the bottom pan with its retained fine aggregate was recorded. The portion of the SCBA sample for sieve analysis was weighed, after drying, approximately 500 grams was weighed to the nearest 0.1 gram. The portion of ballast for test was weighed to the nearest 10 grams on the larger balance except for sieve size less than 4mm which was weighed to 1 gram on the smaller balance

According to AASHTO classification, the notation  $D_{xx}$  refers to the size  $D$ , in mm, for which  $xx$  percent of the sample by weight passes a sieve mesh with an opening equal to  $D$ . The  $D_{10}$  size, sometimes called the **effective grain size**, is the grain diameter for which 10% of the sample (by weight) is finer. The  $D_{50}$  size, called the **median grain size**, is the grain diameter for which half the sample (by weight) is smaller and half is larger. Two parameters are used to describe the general shape of the grain-size distribution curve. Gradation of a soil was determined by calculating the coefficient of uniformity,  $C_u$ , and the coefficient of curvature,  $C_c$ , of the soil and comparing the calculated values with published gradation limits as stipulated by Unified Soil Classification System (USCS).

Muhammad *et al.* (2007) showed that grain size distribution curves can be classified and identified as either log-normal distribution, Talbot distribution or bimodal distribution. They further stated that the grain distribution of aggregates can be classified and identified visually based on the shape of size distribution and size distribution

## **(ii) Hydrometer Analysis**

A sample of fine sand to be used in all the tests was taken from the bottom pan of the sieve set, placed it into a beaker, and 125mL of the dispersing agent (sodium hexametaphosphate (40 g/L)) solution added. The mixture was stirred until the SCBA sample was thoroughly wet and allowed to soak for at least ten minutes. While the SCBA sample was soaking, 125mL of dispersing agent was added into the control cylinder and then filled with distilled water to the mark. The reading at the top of the meniscus formed by the hydrometer stem and the control solution were taken. A reading less than zero was recorded as a negative (-) correction and a reading between zero and sixty were recorded as a positive (+) correction. This reading is called the zero correction. The meniscus correction is the difference between the top of the meniscus and the level of the solution in the control jar (Usually about +1). The control cylinder was shaken in such a way that the contents were mixed thoroughly. Silt content was then determined.

## **(iii) Strength Activity Index Test**

Strength Activity Index (SAI) test, was used to assess the Pozzolanic activity of SCBA. The 7 and 28 days compressive strengths of test mortar was prepared with a 20 % SCBA substitution for cement on a mass basis, these were compared to those of a control mortar. The control mortar was prepared with a water-to-cement ratio by mass ( $w/c$ ) of 0.484, while the water content of the test mixture was adjusted so that there was an equivalent flow to that measured for the control. The SAI of the SCBA samples was determined based on the compressive strength set by the ASTM C311 (2004) specifications. The OPC in the mortar was partially replaced by 20% SCBA and tested. The process used to replace the Portland cements was based on BS 3892 (1997). The

cast iron mould had dimensions 150mm x 150mm with each mortar (1:3 mix) per mould weighing 7Kg. There were 7 specimen specifications prepared; control (cement: sand @ 1:3) and the remaining 6 specimen had SCBA (as shown in Table 1.0) contents with mortar mix cement: SCBA: sand 0.2: 0.8: 3. 3 samples of each specimen were prepared, to cater for 7 and 28days curing period, hence a total of 42 samples.

The Control mortar was prepared by mixing 10.5Kg of OPC and 31.5Kg of Sand and 5.4Kg of water. The test mortar mixture was prepared by mixing 8.4Kg of OPC, 2.1Kg of SCBA and 31.5Kg of sand. The water to binder ratio was altered so that the mixture had the same flow properties as the control mortar ( $\pm 5$  mm). The mortar pastes were mixed for 30 seconds and cast into the moulds with the aid of a vibrating table.

Table 1.0: Test mixtures used in the Strength Activity Tests for different SCBA grain sizes

<b>Mortar Samples</b>	<b>Particle size ( mm)</b>	<b>OPC (Kg)</b>	<b>Sand (Kg)</b>	<b>SCBA (Kg)</b>	<b>Water (Kg)</b>
SAI/Control	No. SCBA	10.5	31.5	0	5.4
D <sub>2</sub>	> 2	8.4	31.5	2.1	5.4
D <sub>1</sub>	2 - 1	8.4	31.5	2.1	5.4
D <sub>0.6</sub>	1 - 0.6	8.4	31.5	2.1	5.7
D <sub>0.3</sub>	0.6 - 0.3	8.4	31.5	2.1	5.8
D <sub>0.15</sub>	0.3 - 0.15	8.4	31.5	2.1	5.8
D <sub>0.075</sub>	0.15 - 0.075	8.4	31.5	2.1	5.8
D <sub>0</sub>	< 0.075	8.4	31.5	2.1	6

A total of 48, 150mm cubes were cast; three for each of the above specimens and tested for 7 and 28 days. After molding, the specimens and moulds were placed in the moist room and maintained  $23 \pm 2^\circ\text{C}$  for 24 hours. Then the cube samples were removed from the moist room, and de-moulded from their respective moulds. The cubes were then placed and stored in



saturated limewater for 1 day. All blocks were de-moulded after 24 hours and placed in a water bath at 23 °C for 6 or 27 days. They were then removed from the bath, surface dried and the compressive strength was tested at 7 and 28 days. The cubes were tested using a universal compression machine (Model: Budensbery - 2000kN) test system with a 2000 KN capacity loading frame. The compressive strength was measured using a constant loading rate of 18 MPa/min.

The average compressive strength was determined from three mortar samples for each specimen at the ages of 7 and 28 days. The results of the total strengths are the averages of the three tests for each sample are presented as percentage strength relative to the control mortar. Therefore, the results are presented as in equation 1.0

$$SAI = A/B \times 100 \dots\dots\dots 1.0$$

Where:

A = Unconfined compressive strength of the test SCBA specimen (Nmm<sup>-2</sup>)

B = Unconfined compressive strength of the control mortar (Nmm<sup>-2</sup>).

According to BS 3892 (1997), SAI results greater than 0.80 after 28 days indicate positive Pozzolanic activity of Pozzolan for a cement replacement of 20%. ASTM C618 (1999) requires a SAI greater than 0.75 after 7 and 28 days for natural Pozzolan at a cement replacement of 20%.

## Results

### (i) Grain Size Distribution of OPC

A distribution of particle sizes or particle size distribution (PSD) is a fundamental characteristic of cement powder. Since there are no standard procedures that adequately cover the broad

particle size range associated with portland cement powder, Chiara *et al* (2004) performed laser diffraction techniques to determine PSD and results stipulated as shown in figure 3.0.

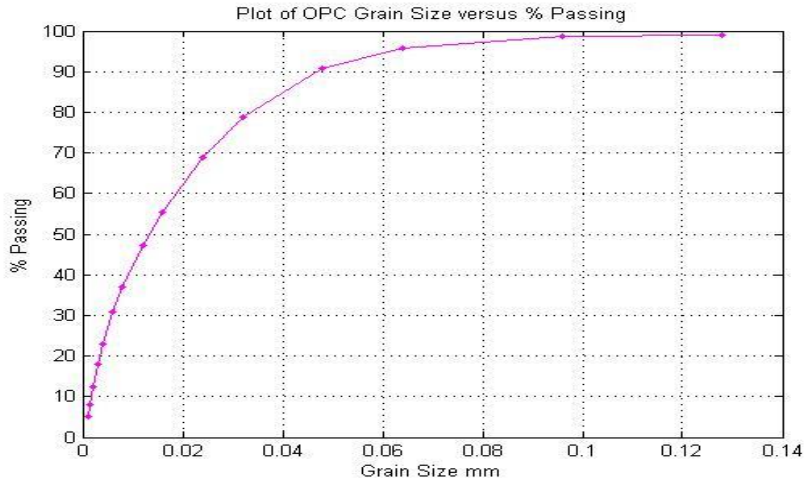


Figure 1.0. Grain size distribution of OPC. Chiara *et al* (2004)

**(ii) Grain Size Distribution SCBA**

Below are PSD curves for different SCBA samples from the 3 dumping sites and a additional one after mixing.

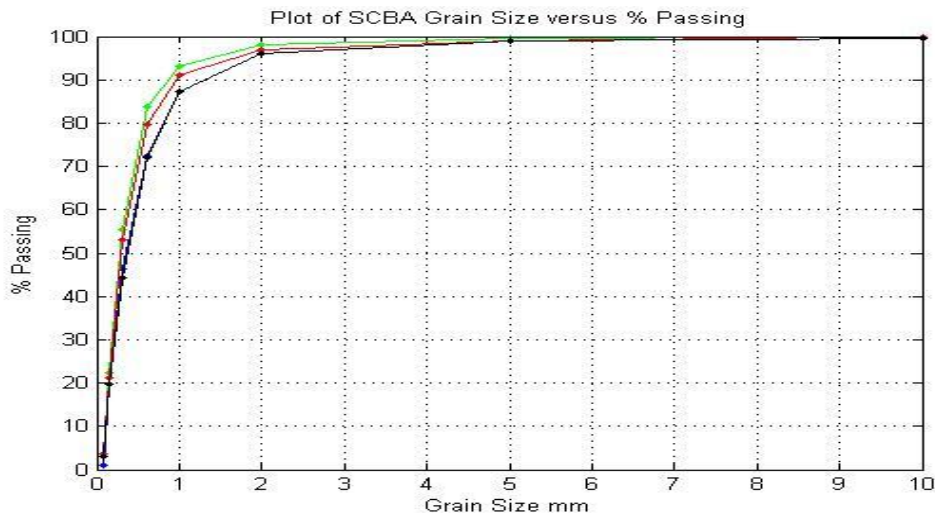


Figure 2.0 PSD of SCBA from the different sites

The grain size distribution and the density curve of both OPC and SCBA exhibit a trend where the density distribution has a single peak, hence can be classified as log-normal distribution.

**Legend**

Green line.....SCBA from site A

Black line.....SCBA from site B

Red line.....SCBA from site C

Blue line..... SCBA from site A, B and C

Based on ASHTOO Classification standards, the *coefficient of uniformity*,  $C_u$  is a crude shape parameter and is calculated using the following equation

$$C_u = D_{60}/D_{10}.....2.0$$

The *coefficient of curvature*,  $C_c$  is a shape parameter and is calculated using the following equation:

$$C_c = (D_{30})^2/ D_{10} \times D_{60}.....3.0$$

SCBA can categorized as semi – fine to fine aggregate (< 5mm), hence according to USCS, the following criteria must be met:

$$C_u \geq 6 \ \& \ 1 < C_c < 3.....4.0$$

If both of these criteria are not met, the grains would be classified as poorly graded or SP. If both of these criteria are met, they would be classified as well graded or SW. Table 2.0 shows classification of OPC and all the SCBA samples including the effective size of particle size distribution (PSD) at 10% ( $D_{10}$ ), 30% ( $D_{30}$ ) and 60% ( $D_{60}$ ) percentage passing.

Table 2.0. Classification of Samples

Sample	D <sub>10</sub> (mm)	D <sub>30</sub> (mm)	D <sub>50</sub> (mm)	D <sub>60</sub> (mm)	C <sub>u</sub>	C <sub>c</sub>	Classification
OPC	0.002	0.007	0.014	0.02	10	1.225	SW
A	0.1	0.25	0.25	0.4	0.4	1.56	SP
B	0.1	0.25	0.45	0.6	6	1.04	SW
C	0.1	0.2	0.3	0.5	5	1.8	SP
D	0.1	0.2	0.45	0.6	6	1.04	SW

**(ii) Strength Activity Index Test Results**

Below is a Table showing SAI results for different SCBA grain sizes at 7 and 28 days curing periods. M1, M2 and M3 denotes the 3 moulds per each specimen and M the average compressive strength. C was the control mix.

Table 3.0 Strength Activity Index Test results of SCBA of different Grain Sizes

	7 days					28 days				
	f <sub>cu</sub> (N/mm <sup>2</sup> )				SAI (%)	f <sub>cu</sub> (N/mm <sup>2</sup> )				SAI (%)
	M1	M2	M3	M	SAI	M1	M2	M3	M	
C	8.8	9.4	9.1	9.1	100	10.1	10.2	10.1	10.1	100
D <sub>2</sub>	5.0	5.0	5.1	5.0	56	4.9	4.8	5.0	4.9	48
D <sub>1</sub>	5.2	5.0	5.1	5.1	56	5.7	5.6	5.7	5.7	56
D <sub>0.6</sub>	5.2	5.3	5.3	5.3	58	6.5	6.6	6.8	6.6	65
D <sub>0.3</sub>	7.2	6.7	6.2	6.7	74	7.0	7.1	7.1	7.1	70
D <sub>0.15</sub>	7.3	7.4	7.5	7.4	81	8.0	8.0	7.9	8.0	79
D <sub>0.075</sub>	8.1	8.1	8.2	8.1	89	8.7	8.6	8.8	8.7	86
D <sub>&lt;0.075</sub>	8.8	8.6	8.7	8.7	96	8.9	9.1	8.7	8.9	88

The above tabulated results were used to develop bar chart presentations of different SCBA grain sizes as shown in Figure 3.0 and 4.0 for SAI test results for mortar samples at 7 and 28 days curing periods, through Matlab R2013a program application and analysis.

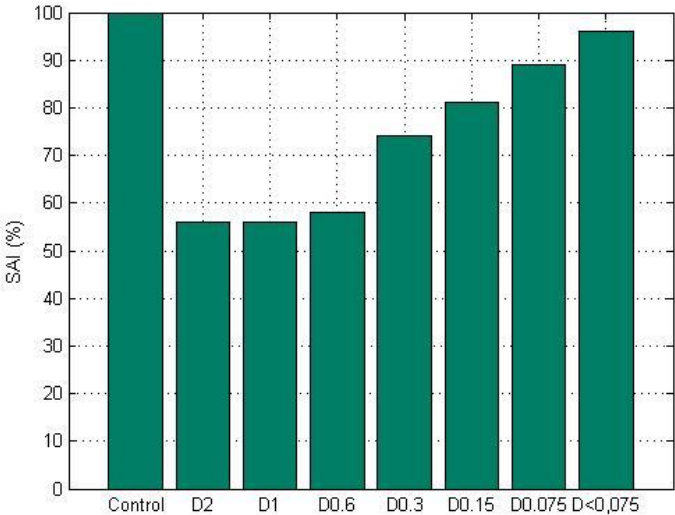


Figure 3.0 Results of SAI test after 7 days

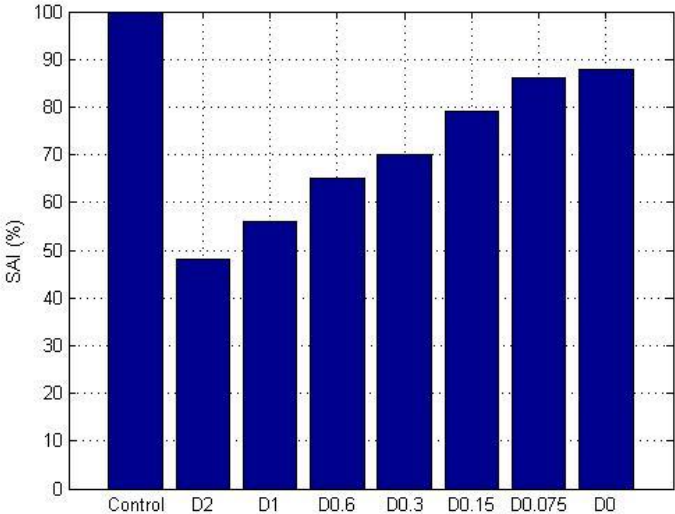


Figure 4.0 Results of SAI test after 28 days

From above figures (3.0 and 4.0), the SAI's of blended mortar increases with decrease in grain size of SCBA. SAI above 75% had SCBA grain sizes retained on sieve sizes 0.15mm, 0.075mm and passing 0.075mm for both seven (7) days and eight (8) curing period.

## **Discussions**

As shown in Figures 3.0 and 4.0, at both curing times of 7 and 28 days, blended mortars with finer SCBA will yield the SAIs well beyond 75%, which is the minimum requirement to classify a material as a Class N pozzolan according to ASTM C618 (2003), this in spite of its meager amorphous  $SO_2$  according to Sirirat and Supaporn (2010). At both curing times, higher SAIs is observed for the fine SCBAs, in agreements with similar trends in similar tests conducted by Torres et al (2014); Bahurudeen and Manu (2014) and several other authors. However filler effect which is to more extent is related to fine size of aggregate in mortar can be said to be a major contributor of higher SAIs, hence a factor considered when designing grain size of OPC. Cordeiro et al. (2010) showed that burning baggase between 400°C and 600°C produces an increase in the Pozzolanic activity index with increasing firing temperatures due to the loss of carbon. The furnace temperature for NSC boilers were around 450°C, however these authors suggest that the optimal temperature for the production of Pozzolanic SCBA is 600°C because at this temperature it is possible to generate predominantly amorphous silica with a SAI of 77%.

## **Conclusions**

SCBA exhibits high Pozzolanic activity, hence can be used as a substitute cementitious material (SCM). The finer the SCBA the higher its Pozzolanic activity, hence it is recommended adopt grain size < 0.015mm to achieve maximum strength in mortars. It is further recommended to study contributory factor of filler effect of SCBA in Pozzolanic activity enhancement in mortars.

The results should help promote the use of industrial SCBAs as an SCM, provided finer particles will be applied thereby enhancing both the filler and the Pozzolanic effects.

## References

- Arkarin A, Preug K, Kannaree C and Thantip P. (2013). Use of Sugarcane Bagasse Ash Raw Material in production of Autoclaved Light-weight Concrete, *Advanced materials Research*. vols. **652-658**. pp. 1242 – 1245, Thailand. Retrieved 15<sup>th</sup> February 2014.
- ASTM C109 (1993). Standard Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. or [50-mm] Cube Specimens). Retrieved 29<sup>th</sup> October 2014.
- ASTM C311. (2004). Standard Test Methods for Sampling and Testing Fly Ash or Natural Pozzolan for Use in Portland-cement Concrete. In: *Annual Book of ASTM Standards*. ASTM International, West Conshohocken, PA, USA, p. 204-212. Retrieved 17 January 2014.
- ASTM C618, (1999). Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete, pp 3. Retrieved 17<sup>th</sup> January 2014.
- ASTM D422 (2007), Standard Test Method for Particle-Size Analysis of Soils. Developed by Subcommittee: D18.03. *Book of Standards Volume: 04.08*. Retrieved 19<sup>th</sup> April 2014.
- Bahurudeen A and Manu S. (2014). Performance Evaluation of Sugarcane Bagasse Ash-Based Cement for Durable Concrete. 4th International Conference on the Durability of Concrete Structures. Purdue University, West Lafayette, IN, USA. Retrieved 10<sup>th</sup> December 2014..
- BS 12, 1996. Specifications for Portland Cement. British Standards Institute, London. 6<sup>th</sup> September 2014
- BS 812-105.1 (1989). Testing aggregates. Methods for determination of particle shape. Flakiness index. Retrieved 23<sup>rd</sup> April 2014.



- BS 882 (1983). Specification for aggregates from natural sources for concrete. Retrieved 23<sup>rd</sup> April 2014.
- BS 3148 (1980). Methods of test for water for making concrete. Retrieved 23<sup>rd</sup> April 2014.
- BS 3892 (1997). Pulverised-fuel ash. Part 1: specification for pulverised fuel ash for use with Portland cement. Retrieved 5<sup>th</sup> September 2014.
- BS 812-119 (1985). Testing aggregates Method for determination of acid-soluble material in fine aggregate. Retrieved 23<sup>rd</sup> April 2014.
- BS EN 196-5 (2011). Methods of testing cement. Pozzolanicity test for Pozzolanic cement. Retrieved 5<sup>th</sup> September 2014.
- Chiara F, Vincent A and Ana I. (2004). Measurement of Particle Size Distribution in Portland Cement Powder: Analysis of ASTM Round Robin Studies.. Cement, Concrete, and Aggregates, Vol. 26, No. 2 Paper ID CCA11920 Available online at: [www.astm.org](http://www.astm.org). Retrieved 18<sup>th</sup> November 2014
- Cordeiro C., Toledo F and Fairbairn R, (2010). Ultrafine sugar cane bagasse ash: high potential pozzolanic material for tropical countries. Laboratory of Civil Engineering, Center of Science and Technology, Universidade Estadual do Norte Fluminense Darcy Ribeiro, gcc@uenf.br, 2000 Av. Alberto Lamago, CEP 28013-602, Campos dos Goytacazes-RJ, Brazil.
- Daniel V, João A and Marcio R. (2011). Effect of Calcination Temperature on the Pozzolanic Activity of Brazilian Sugar Cane Bagasse Ash (SCBA). <http://dx.doi.org/10.1590/S1516-14392014005000093>. Retrieved 5<sup>th</sup> September 2014
- Dubey S, (2011). Concrete Mix Design with Portland Pozzolana Cements. Dept. of Civil Engineering., M.A.N.I.T., Bhopal. Retrieved 11<sup>th</sup> March 2014.

Goyal A, Hattori K, Hidehiko Oa, Monika G, Anwar A, and Ashraf M, (2007). Synergic Effect of Wheat Straw Ash and Rice-Husk Ash on Strength Properties of Mortar. *Journal of Applied Sciences*, 7: 3256-3261. Retrieved 4<sup>th</sup> February 2014.

Muhammad S, Daizo T, Masaharu F and Kunihiko H (2007). Classification of grain size distribution curves of bed material and the porosity. *Annals of Disas. Prev. Res. Int. Kyoto. Univ.*No. 50B. Retrieved 2<sup>nd</sup> January 2014.

Sirirat J and Supaporn W. (2010). Pozzolanic Activity of Industrial Sugar Cane Bagasse ASH. National Metal and Materials Technology Center (MTEC), National Science and Technology Development. Retrieved 20<sup>th</sup> April 2014.

Torres A, Mejía G, Giraldo E and González S(2014). Characterization of sugar cane bagasse ash as supplementary material for Portland cement. *Ingeniería e Investigación*, Vol. 34, No. 1, pp. 5 – 10.